

Title: *Preisach model of hysteresis in magnetic materials and FORC based identification techniques*

Author: Prof. Alexandru STANCU

Address: “Alexandru Ioan Cuza” University, Department of Physics,
Blvd. Carol I, 11
Iasi, 700506, ROMANIA

Email: ALSTANCU@UAIC.RO

Main text:

Preisach model has been used extensively since the model has been initially developed by Ferenc Preisach about 75 years ago, especially for ferromagnetic materials. When the model has been analyzed from a mathematical point of view by Krasnoselskii and Pokrovskii and after them by Mayergoyz and other scientists it was stated that, in fact, the model is “the best hysteresis model at our disposal” (A. Visintin, 1994) to describe any type of hysteretic process. The proven sound mathematical basis gives the model a privileged place among the many hysteresis models available in the scientific literature.

Within the scientific community there is a strong debate concerning the relation between the physical properties of the system and the (Preisach-type) model’s parameters. Some authors argue that the Preisach model is phenomenological in essence (or purely mathematical) which it gives a wide range of applications but offers no possibility to find parameters with physical significance. In this case the model is used as a complex tool to approximate a broad range of experimental data with a limited set of parameters. However, we have to remark that most of the hysteresis models are originated in the effort to explain some concrete physical facts, observed on specific samples, and the building blocks of these models are based on these realities, expressed in a simplified manner in the mathematical formulation of the model. For example, the Classical Preisach Model (CPM) is usually seen as a tool to describe the scalar static magnetization processes in a system of interacting magnetic entities (single domain particles). The effect of interactions is an asymmetry of the rectangular hysteresis loop. In the CPM one assumes that the constitutive entities (named hysterons) are completely characterized by the switching fields that are distributed. Instead of the positive (H_α) and negative (H_β) switching field distributions one uses the distributions of coercive fields $H_c = (H_\alpha - H_\beta)/2$ and interaction fields $H_i = -(H_\alpha + H_\beta)/2$. These two distributions are considered stable (do not change their shape during any magnetization process) and statistically independent. As a consequence, the irreversible Preisach distribution is the product between the two distributions:

$$p_{irr}(H_\alpha, H_\beta) = S p_{ii}(h_i) p_{ic}(h_c) \quad (1)$$

where $p_{ii}(h_i)$ is the Interaction Field Distribution (IFD), $p_{ic}(h_c)$ is the distribution of coercive fields and S is the squareness. The distributions are normalized at the saturation magnetic moment of the sample. We have used a system of axes denoted with (h_c, h_i) and rotated with 45° with respect to the (H_α, H_β) coordinate system ($h_c = \sqrt{2}H_c$ and $h_i = \sqrt{2}H_i$) (see Fig. 1).

Mayergoyz have shown that the necessary and sufficient conditions that should be obeyed by a system to be correctly described by a CPM (CPM systems) are the wiping-out and congruency properties. However, many attempts to find magnetic CPM systems failed. Most of the known magnetic systems do not obey to the congruency property. As a consequence, the CPM has been repeatedly modified in order to provide a modeling solution for the systems showing wiping-out and non-congruency. These “Preisach-type” models, have the origin in the CPM but includes supplementary elements that provide a relaxation of the congruency property. One mention here the well known Moving Preisach Model (MPM) that adds to the statistical interaction field a mean interaction field and the Variable Variance Preisach Model (VVPM) that takes into account the change of the interaction field distribution variance as a function of the magnetic state of the sample..

Micromagnetic simulations made on systems of interacting single domain particles have shown that the mean interaction field and the variable variance are observable in real systems. Moreover, we have shown that the two effects are in fact linked. An essential observation is that we use a model that takes into account the fundamental physical details of the system, even if the primary nature of model is phenomenological, the model's parameters have a clear physical significance. If one uses a model that does not give attention to the physical reality of the system, even if some experimental data measured on the system are correctly fitted by the model, the significance of the parameters becomes difficult to establish.

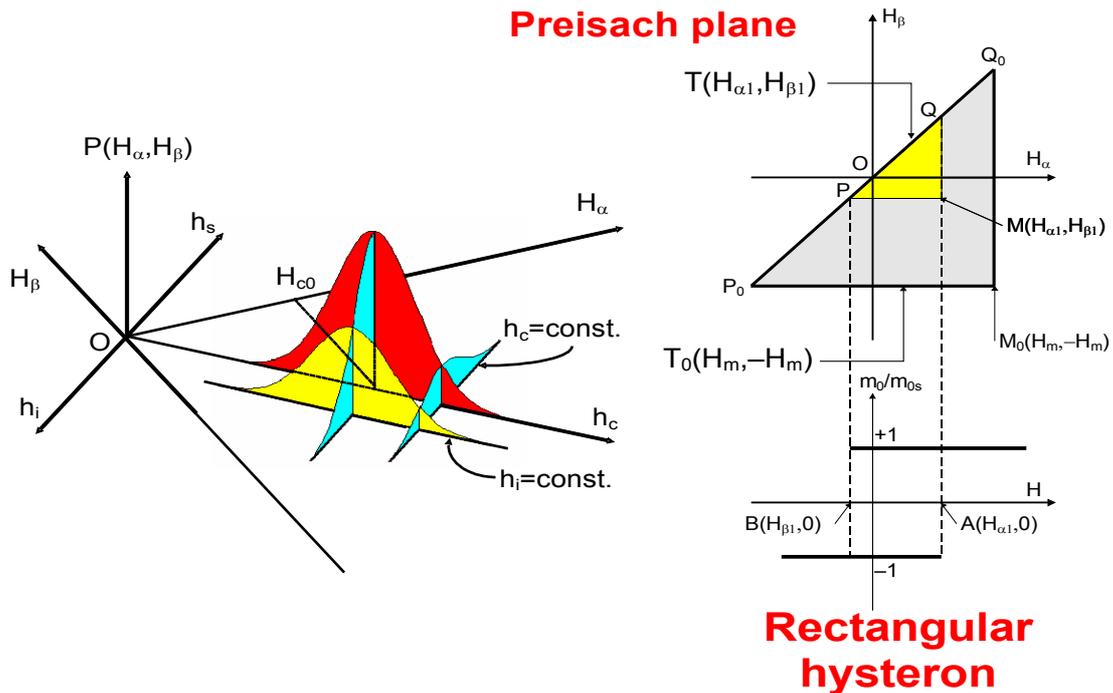


Fig. 1 Preisach plane and Preisach distribution of rectangular hysterons

In this context, we have observed on micromagnetic simulations made on single domain particle systems that in many occasions (especially when the packing ratio was high and particle clusters were observed in the system) the IFD in the DC demagnetized state had a clear two peaks shape. We also have seen that the two peaks shape can be decomposed in a sum of two Gaussian distributions with the amplitudes approximately proportional to the magnetic moment of the sample. At the positive saturation, one distribution has the maximum amplitude and the other one has zero amplitude and in the DC demagnetized state the amplitudes of the two distributions were equal. In the negative saturation the first distribution has zero amplitude and the second one has maximum amplitude. The dependence of the amplitude depends in many cases almost linearly with respect to the magnetic moment of the sample. We have developed a Preisach-type model (Preisach Model for Patterned Media = PM^2 model) that can use the bi-modal Preisach distribution and that contains as particular cases the MPM and VVPM models.

A problem of paramount importance is how we can evaluate the Preisach distribution and the supplementary parameters included in the modified versions of the model. Mayergoyz has designed an identification technique for the classical Preisach model based on a set of First-order Reversal Curves (FORC) curves. As presented in Fig.2, these curves are obtained using a sequence of fields starting from a saturation state. If for simplicity one discuss only the FORCs originated on the descending branch of the Major Hysteresis Loop (MHL) we have to obtain initially the positive

saturation followed by a field decrease down to a field named *reversal field* and then an increase during which the magnetic moment of the sample is measured. The magnetic moment on a FORC will depend consequently on two fields (actual field and reversal field) and the second order mixed derivative of the moment will give a value proportional to the Preisach distribution function.

About a decade ago, Pike and collaborators from University of California Davis proposed the use of the method as a purely experimental tool to obtain a distribution (called FORC distribution) which is characteristic for the measured material. Even if the FORC distribution and the FORC diagram (the contour plot of the distribution) can be obtained rather easily in many laboratories, how to use properly these data is not an easy and straightforward process. Other models are required in order to understand the experimental diagrams obtained. In the lecture we shall present a multitude of aspects related to the proper use of the FORC diagrams in the characterization of magnetic materials.

We also shall show how this method can be extended to the study of another type of hysteretic process (thermal hysteresis in spin-transition materials) in order to emphasize method's generality.

We shall discuss various aspects of the problem, like the FORC diagram symmetry properties, mean field effects observed on the diagram, etc.

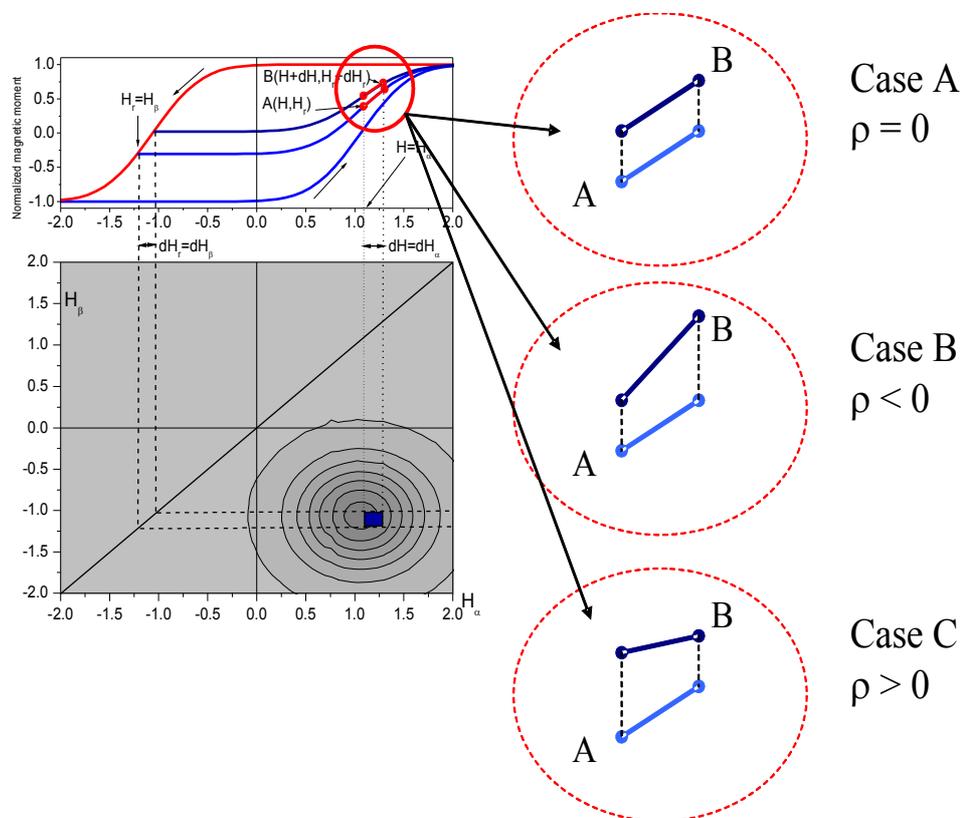


Fig. 2 FORC diagram (ρ = FORC distribution)

References (Preisach model and FORC diagram) :

[1] Author(s): Stancu, A; Bissell, PR; Chantrell, RW

Title: Interparticle interactions in magnetic recording media as obtained from high-order measurements by a Preisach model

Source: JOURNAL OF APPLIED PHYSICS, 87 (12): 8645-8652 JUN 15 2000

[2] Author(s): Andrei, P; Stancu, A

Title: Identification method analyses for the scalar generalized moving Preisach model using major hysteresis loops

Source: IEEE TRANSACTIONS ON MAGNETICS, 36 (4): 1982-1989 Part 2 JUL 2000

[3] Author(s): Stancu, A; Stoleriu, L; Cerchez, M; Postolache, P; Cimpoesu, D; Spinu, L

Title: Standard problems for phenomenological Preisach-type models

Source: PHYSICA B, 306 (1-4): 91-95 DEC 2001

[4] Author(s): Stancu, A; Pike, C; Stoleriu, L; Postolache, P; Cimpoesu, D
Title: Micromagnetic and Preisach analysis of the First Order Reversal Curves (FORC) diagram
Source: JOURNAL OF APPLIED PHYSICS, 93 (10): 6620-6622 Part 2 MAY 15 2003

[5] Author(s): Spinu, L; Stancu, A; Radu, C; Li, F; Wiley, J.B.
Title: Method for magnetic characterization of nanowire structures
Source: IEEE TRANSACTIONS ON MAGNETICS, 40 (4): 2116-2118 JULY 2004

[6] Author(s): Stancu, A; Ricinschi, D; Mitoseriu, L; Postolache, P; Okuyama, M
Title: First-order reversal curves diagrams for the characterization of ferroelectric switching
Source: APPLIED PHYSICS LETTERS, 83 (18): 3767-3769 NOV 3 2003

[7] Author(s): Enachescu, C; Tanasa, R; Stancu, A; Linares, J; Varret, F; Codjovi, E
Title: First Order Reversal Curves (FORC) analysis of Rate Dependent Hysteresis on the example of Light Induced Thermal Hysteresis in a spin-crossover solid
Source: PHYSICAL REVIEW B, 72: Art. No. 054413 2005

[8] Author(s): Tanasa, R; Enachescu, C; Stancu, A; Linares, J; Codjovi, E; Varret, F; Haasnoot, J
Title: First-order reversal curve analysis of spin-transition thermal hysteresis in terms of physical parameter distributions and their correlations
Source: PHYSICAL REVIEW B, 71 (1): Art. No. 014431 JAN 2005

[9] Author(s): Wehland, F; Stancu, A; Rochette, P; Dekkers, MJ; Appel, E;
Title: Experimental evaluation of magnetic interaction in pyrrhotite bearing samples
Source: PHYSICS OF THE EARTH AND PLANETARY INTERIORS, Vol. 153, No. 4, 181-190, 15 DEC 2005

[10] Author(s): Stancu, A; Andrei, P; Stoleriu, L
Title: Magnetic characterization of samples using first- and second-order reversal curve diagrams
Source: JOURNAL OF APPLIED PHYSICS, 99 (8): Art. No. 08D702 APR 15 2006

[11] Author(s): Stoleriu, L; Stancu, A; Mitoseriu, L; Piazza, D; Galassi, C
Title: Analysis of switching properties of porous ferroelectric ceramics by means of first-order reversal curve diagrams
Source: PHYSICAL REVIEW B, 74 (17): Art. No. 174107 NOV 2006

[12] Author(s): Horia Chiriac, Nicoleta Lupu, Laurentiu Stoleriu, Petronel Postolache, Alexandru Stancu
Title: Experimental and micromagnetic first-order reversal curves analysis in NdFeB-based bulk "exchange spring"-type permanent magnets
Source: JOURNAL OF MAGNETISM AND MAGNETIC MATERIALS 316 (2007) 177-180

[13] Author(s): Laurentiu Stoleriu, Petru Andrei, Alexandru Stancu
Title: First Order Reversal Curves Identification Procedures for Vector Models of Hysteresis
Source: JOURNAL OF APPLIED PHYSICS, 103, 07D923 (2008)

[14] Author(s): C. Enachescu; L. Stoleriu; A. Stancu; A. Hauser
Title: Model for elastic relaxation phenomena in finite 2D hexagonal molecular lattices
Source: PHYSICAL REVIEW LETTERS (in press)

books:Recommended

I. D. Mayergoyz, *Mathematical models of hysteresis and their applications*, Amsterdam; Boston: Elsevier, 2003.

G. Bertotti, *Hysteresis in magnetism: for physicists, materials scientists, and engineers*. San Diego: Academic Press, 1998.

E. Della Torre, *Magnetic hysteresis*. New York: IEEE Press, 1999.

M. A. Krasnoselskii and A. V. Pokrovskii, *Systems with hysteresis*. Berlin; New York: Springer-Verlag, 1989.

A. Visintin, *Differential models of hysteresis*. Berlin; New York: Springer, 1994.

A. Stancu, *Magnetization processes modeling*, Ed. Cartea Universitara, Bucharest, 2006.